

Special materials for ophthalmic coating

50
TIGNON

Titanium oxides

- › Highest refractive index in visible range
- › High UV-blockage
- › Good environmental resistance
- › Best reproducibility and lowest thermal stress for coatings on plastics using Ti_3O_5
- › Stable evaporation behaviour without spitting or outgassing
- › Widely tunable refractive index
- › Very good environmental durability
- › Well-suited for BBAR coatings on plastics

Film properties

Refractive index at 550 nm	
› on unheated substrates/no IAD	2.07 – 2.22
› on heated substrates, $T_s = 250\text{ °C}$ /no IAD	2.25 – 2.40
› on unheated substrates/with IAD	2.10 – 2.50
Range of transparency (fully oxidized film)	400 nm – 11 μm
Environmental Stability	MIL-C-675 B/C passed
Stress	
› on unheated substrates/no IAD	Tensile
› on heated substrates, $T_s \geq 250\text{ °C}$ /no IAD	Tensile
› on unheated substrates/with IAD	Type and magnitude depending on IAD parameters

Data based on TiO_2 coatings deposited from Ti_3O_5 starting material.

Low-absorbing films deposited from all titanium oxide starting compositions are of the composition TiO_2 . The structure of the TiO_2 films depends on the deposition conditions and starting materials ranging from amorphous to crystalline anatase or rutile. This explains the wide spread in the refractive index values. TiO_2 films have the highest and most widely tunable refractive index with the best optical contrast to SiO_2 or LIMA™. This enables AR and multilayer coatings with a minimum number of layers. TiO_2 films effectively block UV-radiation for wavelengths < 400 nm which can be used for the protection of the plastic lenses. The stress of TiO_2 films can be tuned in a wide range of tensile and compressive values. Using Ti_3O_5 starting material, thermal stresses on polymeric lenses can be kept at a minimum which makes this material an ideal choice for coatings on polymeric lenses.

LATI™

- › Superior to other lanthania-titania mixtures due to higher material density
- › Complete melting and evaporation without spitting or outgassing
- › Reduced refractive index compared to pure TiO_2 enabling a higher AR bandwidth
- › Strongly reduced structural film stress compared to pure TiO_2
- › Close-to-zero compressive-type stress possible without ion assistance
- › Very good thickness homogeneity and run-to-run stability
- › Direct adhesion to certain polymeric substrate types

Film properties

Refractive index at 550 nm	
› on unheated substrates/no IAD	1.90 – 2.02
› on unheated substrates/with IAD	2.04 – 2.08
› on heated substrates, $T_s = 300\text{ °C}$	2.09 – 2.12
Range of transparency	380 nm – 7.0 μm
Environmental Stability	MIL-C-675 B/C passed
Stress	Type and magnitude depending on deposition parameters

Film stress of LATI™ is smaller than for TiO_2 and its type and magnitude are variable by the choice of the process parameters. Films with close-to-zero compressive-type stress can be obtained by conventional deposition. LATI™ films are well-adhering to a number of substrate types (especially certain types of plastics) and show a good environmental stability. Due to these properties LATI™ is used as the H-index material in AR or other dielectric coatings especially on plastics, partly in combination with DRALO™.

Application Guidelines


Characteristics of starting material

Chemical formula	TiO	Ti_2O_3	Ti_3O_5	$TiO_{2.3x}$	TiO_2
Color	Gold	Purple	Black-purple	Black, white	
Density g/cm^3	4.9	4.6	4.6	4.2	
Melting point $^{\circ}C$	1750	~ 1760	~ 1760	1775	
Form	Tablets, granulate				

Evaporation technique

All titanium oxides melt completely. Only the Ti_3O_5 melt evaporates congruently. Titanium oxides are deposited reactively by electron beam evaporation from a Cu-crucible with Mo-liner or from Mo-boats.

Typical deposition in all sizes of coating systems involves rates of 0.2 – 0.5 nm/s at O_2 pressures of $2 - 3 \times 10^{-4}$ mbar (or equivalent O_2 flow). The intended values of refractive index and film stress can be obtained by variation of substrate temperature, oxygen pressure or flow, deposition rate and the parameters of ion assistance (IAD). O_2 operated RF plasma ion sources are able to produce high-dense TiO_2 films with full stress compensation relative to SiO_2 .

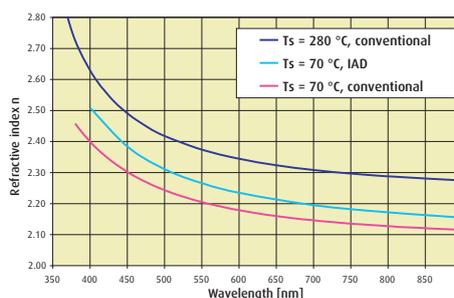

Typical dispersions of the refractive index of TiO_2 films for the indicated deposition conditions. IAD parameters for coatings on plastic substrates.

Application Guidelines


Characteristics of starting material

Chemical formula	La-Ti-oxide
Color	Dark grey with slight metallic appearance
Density g/cm^3	5.9 – 6.2
Melting point $^{\circ}C$	~ 1800
Form	Granulate

Evaporation technique

LATI™ is typically evaporated by reactive electron beam evaporation with or without ion assistance. Typical deposition in all coating systems with maximum coating distance of 900 mm involves rates 0.3 – 0.5 nm/s and O_2 pressures of 3×10^{-4} mbar (or equivalent O_2 flow). The intended values of refractive index and film stress can be obtained by variation of substrate temperature, oxygen pressure or flow, deposition rate and the parameters of ion assistance.

Using LATI™ instead of pure titanium oxides requires to follow some particular guidelines to obtain reproducible, well-homogeneous films.

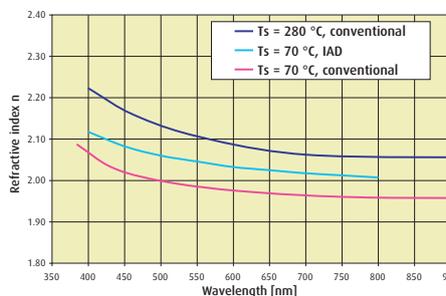

Typical dispersions of the refractive index of LATI™ films for the indicated deposition conditions. IAD parameters for coatings on plastic substrates.

DRALO™

- › Reduced refractive index compared to pure TiO₂, enabling a higher AR bandwidth
- › Effective protection against UV radiation
- › Widely tunable film stress from tensile to compressive values
- › Reduced structural film stress compared to pure TiO₂
- › Optimized thermal film stress on plastics compared to pure TiO₂
- › Very good thickness homogeneity and run-to-run stability
- › Excellent environmental durability
- › Very good resistance against combined attack of heat, humidity and UV-radiation
- › Controlled water barrier

Film properties

Refractive index at 550 nm	
› on unheated substrates/no IAD	2.04 – 2.18
› on heated substrates, T _s ≥ 250 °C/no IAD	2.26 – 2.28
› on unheated substrates/with IAD	2.05 – 2.30
Range of transparency (fully oxidized film)	400 nm – 7.0 µm
Environmental Stability	MIL-C-675 B/C passed
Stress	
› on unheated substrates/no IAD	Mostly tensile depending on rate and O ₂ pressure
› on heated substrates, T _s ≥ 250 °C/no IAD	Tensile
› on unheated substrates/with IAD	Type depending on IAD parameters

These properties make DRALO™ layers especially well-suited as the high-index material in AR coatings for polymeric substrates such as ophthalmic lenses.

Application Guidelines


Characteristics of starting material

Chemical formula	Ti-Al-oxide
Color	Black metallic
Density g/cm ³	4.5
Melting point °C	1700
Form	Granulate

Evaporation technique

DRALO™ films can be produced by reactive electron beam evaporation using Cu-crucibles with Mo-liners. Typical deposition in all sizes of coating systems involves O₂ pressures of ~3 x 10⁻⁴ mbar (or equivalent O₂ flow) and rates 0.2 – 0.4 nm/s. The intended values of refractive index and film stress can be obtained by variation of substrate temperature, oxygen pressure or flow, deposition rate and the parameters of ion assistance.

Using DRALO™ instead of pure titanium oxides requires to follow some particular guidelines to obtain reproducible, well-homogeneous films.

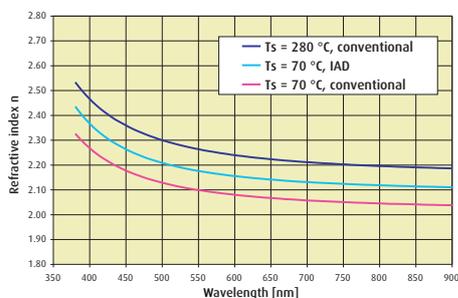

Typical dispersions of the refractive index of DRALO™ films for the indicated deposition conditions. IAD parameters for coatings on plastic substrates.


Zirconium oxides

- › Hard and durable films
- › H-index material for AR coatings especially on plastics
- › ZrO starting material with higher density and complete melting for easier evaporation

Film properties

Refractive index at 550 nm	
› on unheated substrates/no IAD	1.92 – 1.97
› on unheated substrates/with IAD	1.95 – 2.05
› on heated substrates, T _s = 300 °C	2.00 – 2.07
Range of transparency	350 nm – 7.0 µm
Environmental Stability	MIL-C-675 B/C passed
Stress	
› without IAD	Tensile
› on unheated substrates/with IAD	Tunable type and magnitude

Regardless to the starting material composition, low-absorbing zirconia films are of the composition ZrO₂. Such films are hard and durable and they can be used in AR coatings – partly along with thin layers of TiO₂ or DRALO™ to adjust the reflection characteristic.

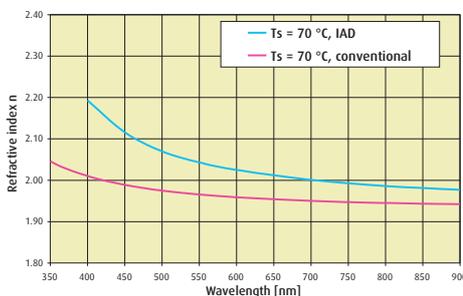

Typical dispersions of the refractive index of ZrO₂ films for the indicated deposition conditions. IAD parameters for coatings on plastic substrates.

Application Guidelines

Characteristics of starting material

Available as zirconium dioxide ZrO₂ (with or without minor deficiency x of oxygen) or zirconium monoxide ZrO.

Chemical formula	ZrO ₂	ZrO _{2-x}	ZrO
Color	White	Grey-black	Dark grey to black
Density	5.6	5.6	6.4
Melting point °C	~ 2700	~ 2700	~ 2200
Form	Tablets, granulate		

Evaporation technique

Zirconium oxides are mostly evaporated by reactive e-beam evaporation from a Cu-crucible with Mo-liner. Zirconium dioxide ZrO₂ melts only superficially and predominantly sublimates. Therefore it requires a very uniform beam pattern to avoid craters and uniformity problems. ZrO is fully melting and can be used to prevent such problems. It can also be evaporated from W-boat. The intended values of refractive index and film stress can be obtained by variation of substrate temperature, oxygen pressure or flow, deposition rate and the parameters of ion assistance.

Deposition occurs typically at O₂ pressures of 1 – 3 x 10⁻⁴ mbar (or equivalent O₂ flow) for ZrO₂/ZrO_{2-x} and 2 – 3 x 10⁻⁴ mbar (or equivalent O₂ flow) for ZrO. Typical deposition in all sizes of coating systems involves rates 0.2 – 0.5 nm/s. The tendency to inhomogeneity can be counteracted using IAD.

Zr-Ti-oxides

- › Zr-Ti-oxide tablets show a stable evaporation behaviour without spitting or outgassing
- › Optimized film stress compared to pure ZrO₂ and TiO₂ films
- › Widely tunable refractive index n
- › Very good environmental durability
- › Well-suited for BBAR coatings on plastics with refractive indices n > 1.60

Film properties

Refractive index at 550 nm	
› on unheated substrates/no IAD	1.80 – 1.88
› on heated substrates, T _s ≥ 250 °C/no IAD	2.01 – 2.03 (2.10 at 300 °C)
› on unheated substrates/with IAD	1.94 – 1.96

Range of transparency (fully oxidized film) 400 nm – 11 µm

Environmental Stability MIL-C-675 B/C passed

Stress

› on unheated substrates/no IAD	Tensile
› on heated substrates, T _s ≥ 250 °C/no IAD	Tensile
› on unheated substrates/with IAD	Tensile

Thin films made from Zr-Ti-oxide effectively block UV-radiation for wavelengths < 240 nm. Compared to pure ZrO₂ and TiO₂ films, Zr-Ti-oxide films have a reduced tensile film stress. Refractive index and reduced mechanical stress of Zr-Ti-oxide films made from Zr-Ti-oxide source material by conventional or slightly assisted deposition without substrate heating makes this material a good choice for coatings on plastics with refractive indices n > 1.60.

Zr-Ti-oxide with higher refractive index is available.

Application Guidelines


Characteristics of starting material

Chemical formula	Zr-Ti-oxide
Color	Black to dark gray
Density g/cm ³	~ 5.1
Melting point °C	~ 1850
Form	Tablets, granulate

Evaporation technique

Zr-Ti-oxide films can be produced by reactive deposition from Zr-Ti-oxide tablets by electron beam evaporation using water cooled Cu-crucibles with Mo-liners. Typical deposition in all coating systems with maximum coating distance of 900 mm involves O₂ pressures of ~3 x 10⁻⁴ mbar (or equivalent O₂ flow) and rates 0.2 – 0.4 nm/s. The intended values of refractive index and film stress can be obtained by variation of substrate temperature, oxygen pressure or flow, deposition rate and the parameters of ion assistance.

Using Zr-Ti-oxide instead of pure zirconium oxide requires to follow some particular guidelines to obtain reproducible, well-homogeneous films.

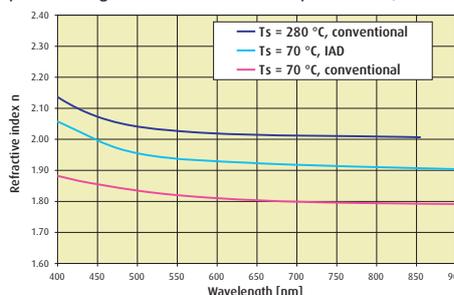

Typical dispersions of the refractive index of Zr-Ti-oxide films for the indicated deposition conditions. IAD parameters for coatings on plastic substrates.

ROMA™

- › Stable evaporation behaviour without spitting or outgassing
- › Yields homogeneous layers in contrast to pure ZrO₂ and an improved oxidation behaviour relative to Ta₂O₅
- › Optimized film stress compared to pure ZrO₂ films
- › Moisture barrier leading to considerably increased environmental durability
- › Well-suited for BBAR coatings on plastics

Film properties

Refractive index at 550 nm	
› on heated substrates, T _s ≥ 250 °C/no IAD	2.04 – 2.07
› on unheated substrates/with IAD	1.85 – 2.10

Range of transparency (fully oxidized film) 350 nm – 10 µm

Environmental Stability MIL-C-675 B/C passed

Stress

› on heated substrates, T _s ≥ 250 °C/no IAD	Depending on deposition conditions
› on unheated substrates/with IAD	Tensile

ROMA™ has been designed to yield very homogeneous layers in contrast to pure ZrO₂ and an improved oxidation behaviour relative to Ta₂O₅. ROMA™ films also show a considerably improved climate test resistance due to their increased water impermeability.

Thin films made from ROMA™ effectively block UV-radiation for wavelengths < 350 nm. Compared to pure ZrO₂ films, ROMA™ films have a reduced tensile film stress. Refractive index, reduced mechanical stress and environmental durability of ROMA™ films from assisted deposition without substrate heating makes this material a good choice for coatings on plastics.

Application Guidelines


Characteristics of starting material

Chemical formula	Zr-Ta-oxide
Color	Black to dark gray
Density g/cm ³	~ 6.82
Melting point °C	~ 2100
Form	Tablets, granulate

Evaporation technique

ROMA™ films can be produced by reactive electron beam evaporation using water cooled Cu-crucibles with Mo-liners. Typical deposition in all sizes of coating systems involves rates of 0.2 – 0.4 nm/s at O₂ pressures of 2 – 4 x 10⁻⁴ mbar (or equivalent O₂ flow) at increased substrate temperature or with ion assistance. The intended values of refractive index and film stress can be obtained by variation of substrate temperature, oxygen pressure or flow, deposition rate and the parameters of ion assistance.

For ROMA™ containing coatings on plastic lenses ion assistance is indispensable to obtain low-absorbing layers. Using ROMA™ instead of pure zirconium or tantalum oxide requires to follow some particular guidelines to obtain reproducible, low-absorbing and well-homogeneous films.

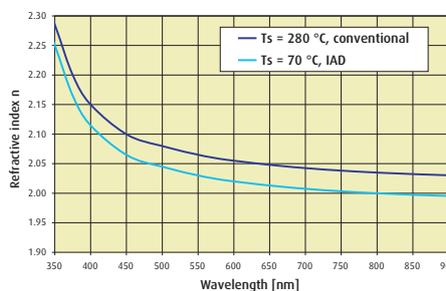

Typical dispersions of the refractive index of ROMA™ films for the indicated deposition conditions. IAD parameters for coatings on plastic substrates.

LIMA™

- › L-index material for AR coatings especially on plastics
- › Refractive index and hardness similar to SiO₂
- › Optimized water impermeability compared to SiO₂
- › Higher environmental durability than SiO₂

Film properties

Refractive index at 550 nm	~ 1.48
› on unheated substrates/no IAD	
Range of transparency (fully oxidized film)	190 nm – 9.0 μm
Environmental Stability	MIL-C-675 B/C passed
Stress	
› on unheated substrates/no IAD	Mostly compressive
› on unheated substrates/with IAD	Compressive

LIMA™ films have optical properties (refractive index, transmission range) and mechanical properties (hardness, stress) that are similar to those of pure SiO₂. LIMA™ is designed to obtain films with water impermeability that leads to an increased resistance against environmental impact. For certain coating conditions, LIMA™ films exhibit smaller values of compressive stress than films of pure SiO₂.

ITO

- › Transparent conductive material for conducting or antistatic function
- › Antistatic function complements easy-to-clean coatings on AR and color coatings
- › Additional function as adhesion promoter for use as the first layer
- › Inhouse raw material source and recycling capabilities

Film properties

Refractive index at 550 nm	1.9 – 2.2
Range of transparency (T ≥ 80%)	~400 nm – ~1.1 μm
Sheet resistance	Ω/sq to the MΩ/sq-range
Environmental Stability	MIL-C-675 B/C passed

Low-absorbing ITO films are transparent in the visible and near-infrared spectral ranges, but strongly reflecting in the IR range. Depending on the In-/Sn-oxide ratio and the deposition conditions, ITO films can be electrically conductive with sheet resistances from the Ω/sq to the MΩ/sq-range. Resistances in the kΩ/sq-range are enough for an antistatic effect and can be achieved with an ITO thickness of only a few nanometers.

The ratio of transmittance in the visible range and conductivity can be adjusted by post-deposition thermal treatment in vacuum or air (increase or decrease of conductivity, respectively).

For coatings on plastics, for example AR coatings on eyeglasses, the absorption of ITO for an unassisted deposition can be compromised by the small layer thickness. Also, it can be improved by ion assisted deposition.

Application Guidelines


Characteristics of starting material

Chemical formula	Si-Al-oxide
Color	White to light grey
Density g/cm ³	2.25
Melting point °C	~ 1730
Form	Tablets, granulate

Evaporation technique

LIMA™ predominantly sublimates. LIMA™ films are deposited by reactive or non-reactive electron beam evaporation using Cu-crucibles with Mo-liners. Typical deposition rates are 0.5 – 2.0 nm/s. The intended values of refractive index and film stress can be obtained by variation of substrate temperature, oxygen pressure or flow, deposition rate and the parameters of ion assistance. Post-deposition treatment of the last LIMA™ layer with ion assistance can be used to increase the climate resistance of the film stack.

Using LIMA™ instead of pure SiO₂ requires to follow some particular guidelines to obtain reproducible, well-homogeneous films.

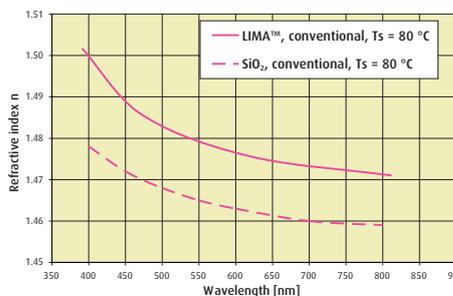

Typical dispersions of the refractive index of LIMA™ films for the indicated deposition conditions.

Application Guidelines

Characteristics of starting material

Chemical formula	In-Sn-oxide
Color	Steel-grey to green
Density g/cm ³	~ 7.1 (In-/Sn-oxide 90/10)
Melting point °C	~ 1730
Form	Tablets, granulate


The material can be supplied in different ratios In-/Sn-oxide from 83/17 to 95/5 %wt.

Evaporation technique

ITO fully sublimates. ITO films are deposited by reactive or non-reactive electron beam evaporation using Cu-crucibles with Mo-liners or thermal evaporation using Mo-boats with cover.

The refractive index of ITO films, the degree of transmittance in the VIS, the onset of reflectance in the IR spectral range and the conductivity can be tuned using the composition of the starting material or the deposition parameters like temperature, oxygen pressure and the parameters of ion assistance.

To obtain the required low absorption for ITO films in coatings on plastics it is possible to use either a very small layer thickness or ion assistance with an O₂ flow through the ion source.

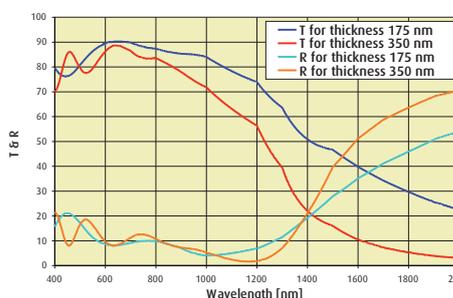

Typical transmittance and reflectance spectra for ITO.

Color materials

- › Color tinting of ophthalmic lenses without wet chemistry
- › Good UV protection
- › Precise controllability of light intensity and UV blockage independently from substrate curvature and thickness
- › Adhesion promotion for coating stack
- › Possible combination with AR coating
- › Partly for plastics with refractive indices $n > 1.60$


Material	Color	Transmittance % at 550 nm	Form	Application notes
Absorption color				
MALBUNIT™ F1	 Brown	20 – 80	Fine granulate	Flash coating, W-boat
MALBUNIT™ F1G	 Brown	20 – 80	Fine granulate	Flash coating, W-boat
MALBUNIT™ F10	 Brown	20 – 80	Fine granulate	Flash coating, W-boat
MALBUNIT™ F13	 Brown	20 – 80	Fine granulate	Flash coating, W-boat
MALBUNIT™ F23	 Brown	20 – 80	Fine granulate	Flash coating, W-boat
MALBUNIT™ F24	 Brown	20 – 80	Fine granulate	Flash coating, W-boat
MALBUNIT™ 8/1	 Brown	20 – 80	Granulate, tablets	E-beam graphite-liner, W-boat
MALBUNIT™ G	 Brown	20 – 80	Fine granulate	Flash coating, e-beam Mo-liner, W-boat
MELDINA™ III	 Brown	20 – 80	Fine granulate	Flash coating, e-beam Mo-liner
MELDINA™ V	 Brown	20 – 80	Fine granulate	Flash coating, e-beam Mo-liner
MELDINA™ TAB	 Brown	20 – 80	Tablets, discs	E-beam Mo-liner
MELDINA™ H	 Brown	20 – 80	Discs	E-beam Mo-liner
MG51™	 Grey	20 – 80	Powder	Mo-boat, e-beam Mo-liner
GREY A™	 Grey	20 – 80	Granulate	W-boat
OLIVIN™ C1	 Blue*		Tablets	Mo-boat, special guidelines
OLIVIN™ C2	 Yellow		Granulate	Mo-boat
OLIVIN™ C1 + OLIVIN™ C2	 Green*		s. OLIVIN™ C1 + OLIVIN™ C2	Mo-boat, multilayer, special guidelines

Reflected color				
Cr + SiO (FLEXO)	 Silver		Cr granulate, SiO granulate, tablets	E-beam, Mo-liner, Cr 60 nm, SiO 20 nm
Cr + SiO (FLEXO)	 Bronze		Cr granulate, SiO granulate, tablets	E-beam, Mo-liner, Cr 60 nm, SiO 50 nm
Cr + SiO (FLEXO)	 Blue		Cr granulate, SiO granulate, tablets	E-beam, Mo-liner, Cr 60 nm, SiO 80 nm
Cr + SiO (FLEXO)	 Green-Yellow		Cr granulate, SiO granulate, tablets	E-beam, Mo-liner, Cr 60 nm, SiO 150 nm
Cr + SiO (FLEXO)	 Gold		Cr granulate, SiO granulate, tablets	E-beam, Mo-liner, Cr 60 nm, SiO 180 nm
Cr + SiO (FLEXO)	 Violet		Cr granulate, SiO granulate, tablets	E-beam, Mo-liner, Cr 60 nm, SiO 240 nm
Cr + SiO (FLEXO)	 Green		Cr granulate, SiO granulate, tablets	E-beam, Mo-liner, Cr 60 nm, SiO 300 nm


Reflected/transmitted color				
TiO ₂ + SiO ₂	All colors, non absorbing layers	Depending on thicknesses and color	TiO ₂ : s. Titanium oxides, SiO ₂ : Granulate, discs	E-beam, Mo-liner, HL-alternating dielectric stack or combination with absorbing material

The indicated color tones for MALBUNIT™ and MELDINA™ are obtained for same film thickness of ~ 300 nm.

* For mineral glass only.

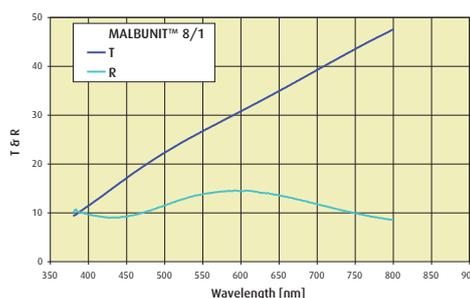

Typical transmittance and reflectance spectra for MALBUNIT™ 8/1.

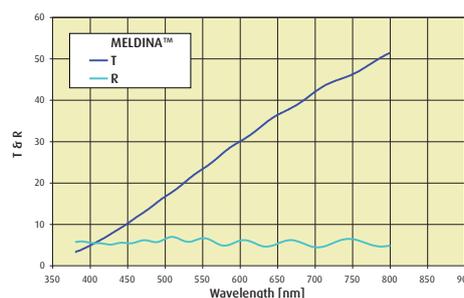

Typical transmittance and reflectance spectra for MELDINA™.

Hydrophobic materials

- › **HYDROPHOBIC™ or TOPCOAT™ films make coated lenses water and dirt repellent**
- › **HYDROPHOBIC™ or TOPCOAT™ films ease the cleaning of eyeglasses**
- › **HYDROPHOBIC™ or TOPCOAT™ films can be complemented by antistatic layers for higher cleaning comfort**
- › **Lenses with HYDROPHOBIC™ or TOPCOAT™ films can be easily processed after coating**
- › **HYDROPHOBIC™ or TOPCOAT™ films show a very abrasion-resistant hydrophobic effect**

Film properties

Cleaning properties	as-deposited	after abrasion testing
CA water [°]	107 – 111	104 – 106

Optical properties

Refractive index at 550 nm	1.36 – 1.46 depending on deposition conditions and thickness
Range of transparency	Visible range

HYDROPHOBIC™ or TOPCOAT™ films have very good hydrophobic properties thus providing a good cleaning comfort. These properties are very resistant to abrasion. Also, HYDROPHOBIC™ or TOPCOAT™ films are of reduced slippery thus enabling all post-deposition processing steps without additional adhesion layers or additional pads.

HYDROPHOBIC™ or TOPCOAT™ films are optically transparent and have an optical index that is close to that for SiO₂. Therefore, the change in the reflective color of an AR coating is small but it has sometimes to be compensated for in the optical design.

Application Guidelines

Characteristics of starting material

Name	HYDROPHOBIC™/TOPCOAT™
Color	White
Density g/cm ³	~ 1.0
Z-Ratio	1.00
Tooling	1.00
Evaporation temperature °C	~ 300
Form	Tablets

The material can be supplied in different sizes and with customized amounts of hydrophobic substance.

Evaporation technique

Films from HYDROPHOBIC™ or TOPCOAT™ tablets are applicable to coatings with SiO₂ or LIMA™ as the last layer. Minimum film thicknesses for optimum hydrophobic function is ~25 nm for the nominal density indicated in the table.

Deposition is possible from a resistively heated Mo-boat or a spiral heater as well as by electron beam evaporation using a topcoat liner. Typically, coating is done in constant power mode. Special guidelines apply to each of these techniques.

The material is in use on table coaters and on a wide range of box coater types.

Superhydrophobic and oleophobic materials

- › **EVERCLEAN™ superhydrophobic and oleophobic films make coated lenses water, oil and grease repellent**
- › **EVERCLEAN™ films give the highest possible cleaning comfort for coated lenses**
- › **EVERCLEAN™ topcoat can be complemented by antistatic layers for higher cleaning comfort**
- › **EVERCLEAN™ is very resistant to abrasion and combined action of UV, humidity and temperature**
- › **EVERCLEAN™ tablets have a shelf life time > 1.5 years**

Film properties

Cleaning properties	as-deposited	after abrasion testing	after QUV ageing
CA water [°]	112 – 118	108 – 112	~ 100
CA angle n-hexadecane [°]	68 – 71	68 – 70	~ 51
Cleanability	1	1 – 2	1 – 3

Post-deposition processing properties

Gliding angle [°]	8 – 10
Slippage [°] for ~ 2.00 diop lens, single pad	1 – 2

Optical properties

Refractive index at 550 nm	1.36 – 1.46 depending on deposition conditions and thickness
Range of transparency	Visible range

EVERCLEAN™ films are at the chemically achievable limit for water, oil and grease repulsion and therefore give the highest available cleaning comfort. The films are very resistant against abrasion and QUV weathering.

EVERCLEAN™ coated lenses show good adhesion of the marking ink for the positioning pattern. Due to their strongly reduced slipperiness, they can be processed without any additional adhesion layers for better pad adhesion or additional pads.

The optical index of EVERCLEAN™ films is close to SiO₂. Therefore, the change in the reflective color of an AR coating is small but it has sometimes to be compensated for in the optical design.

Application Guidelines

Characteristics of starting material

Name	EVERCLEAN™
Color	White
Density g/cm ³	~ 1.0
Z-Ratio	1.00
Tooling	1.00
Evaporation temperature °C	~ 300
Form	Tablets

The material can be supplied in different sizes and with customized amounts of hydrophobic substance.

Evaporation technique

Films from EVERCLEAN™ tablets are applicable to coatings with SiO₂ or LIMA™ as the last layer. Minimum film thicknesses for optimum hydrophobic function is ~25 nm for the nominal density indicated in the table.

Deposition is possible from a resistively heated Mo-boat or a spiral heater as well as by electron beam evaporation using a topcoat liner. Typically, coating is done in constant power mode. Special guidelines apply to each of these techniques.

The material is in use on table coaters and on a wide range of box coater types.

